



Thermal and Combustion Characteristics of Polyacrylonitrile Containing Covalently-bound Phosphonate Groups

Tretsiakova-McNally, S., & Joseph, P. (in press). Thermal and Combustion Characteristics of Polyacrylonitrile Containing Covalently-bound Phosphonate Groups. In *Unknown Host Publication* University of Central Lancashire.

[Link to publication record in Ulster University Research Portal](#)

Published in:
Unknown Host Publication

Publication Status:
Accepted/In press: 27/03/2017

Document Version
Publisher's PDF, also known as Version of record

General rights
Copyright for the publications made accessible via Ulster University's Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy
The Research Portal is Ulster University's institutional repository that provides access to Ulster's research outputs. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact pure-support@ulster.ac.uk.

also gave the values for the maximum amount of heat released per unit mass per degree of temperature, i.e. heat release capacity measured in $\text{kJg}^{-1}\text{K}^{-1}$, and this can be considered as a reliable indicator regarding flammability of a material [5].

Results

The results of TGA indicated noticeable differences between thermograms (obtained in nitrogen and in air) of PAN and the copolymers, even of those containing only minimal amount of modifying groups. The amounts of char residue produced at 700°C , in both atmospheres, were significantly higher for the copolymers, as opposed to PAN, suggesting an occurrence of a condensed phase activity of phosphonate groups.

The PCFC data confirmed the flame-retardant effect of modifying groups attached to the PAN chains. For example, the introduction of phosphonate units into the polymer backbone reduces the HRR values (Figure 1). The other parameters such as the peak Rate of Heat Release (RHR), Total Heat Released (THR) and Heat Release (HR) capacity values were also found to be reduced for the copolymers. Indeed, the incorporation of DE1AEP groups led to a decrease in HR capacity from $200.7 \text{ kJg}^{-1}\text{K}^{-1}$ for PAN to $102.1 \text{ kJg}^{-1}\text{K}^{-1}$ for poly(AN-co-DE1AEP) containing 4 wt. % of P. Therefore, it can be concluded that the incorporation of covalently-bound P-containing groups in PAN modified its thermal degradation behaviour and also resulted in an enhancement of the fire retardance.

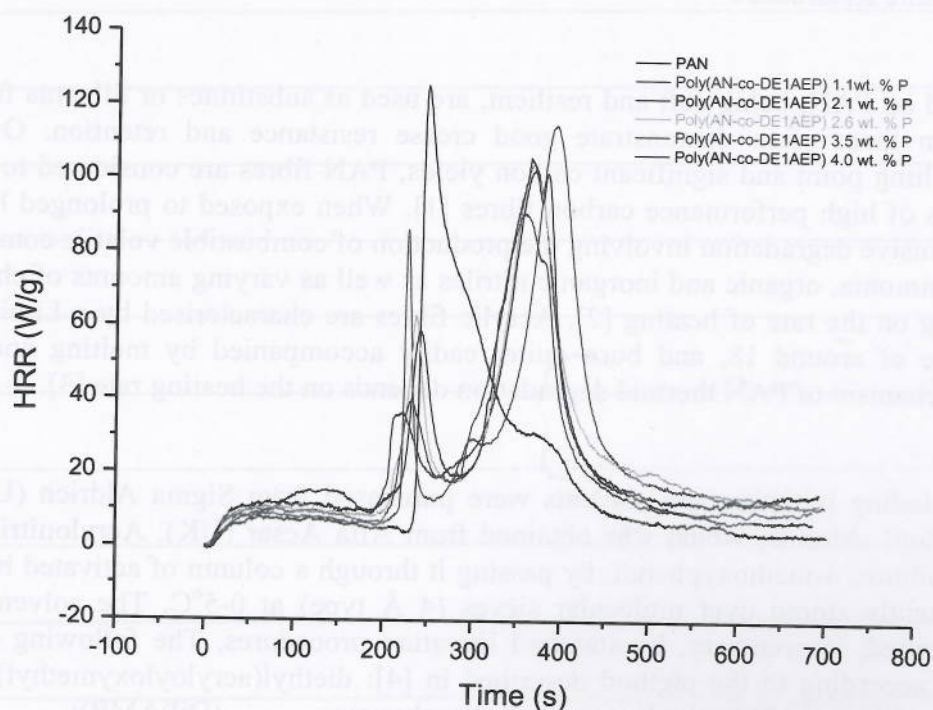


FIGURE 1. Heat Release Rate (HRR) versus time for samples of PAN and poly(AN-co-DE1AEP) containing various amount of phosphorus.

References

1. P. Joseph; S. Tretsiakova-McNally 'Mechanistic Aspects of Flame Retardation by Phosphorus-Containing Groups of Some Chain Growth Polymers', in *Fire and Polymers VI: New Advances in Flame Retardant Chemistry and Science*, Ed., A. B. Morgan et al., Washington DC: American Chemical Society, 2012, pp. 38-50.
2. M. E. Hall; A. R. Horrocks; J. Zhang, The flammability of polycrylonitrile and its copolymers. *Polym. Degrad. Stab.* 1994, 44, 379.
3. P. Joseph; S. Tretsiakova-McNally, Combustion behaviours of chemically modified polyacrylonitrile polymers containing phosphorylamino groups. *Polym. Degrad. Stab.* 2012, 97, 2531.
4. R. Liepins et al., Localized radiation grafting of flame retardants to polyethylene terephthalate. II. Vinyl phosphonates. *J. Appl. Polym. Sci.* 1978, 22, 2403.
5. R. E. Lyon; R. N. Walters, Pyrolysis combustion flow calorimetry. *J. Anal. Appl. Pyrolysis.* 2004, 71, 27.